

Production and Characterization of Fire-Retardant Coating Materials Using Gum Arabic for Cellulose Surfaces

¹Temiloluwa Ojuolape Amusan, ²Jonathan Maduka Nwaedozi and ²Femi Emmanuel Awe

¹Department of Chemistry, Airforce Institute of Technology, Kaduna 800283, Nigeria

²Department of Chemistry, Nigeria Defense Academy, Kaduna 800283, Nigeria

ABSTRACT

Background and Objective: Fire retardants are substances that are applied to the surface of any combustible base which can delay the spread of fire or keep the structure intact against fire, thereby allowing sufficient time for safety measures to be taken. In this study, the production and chemical characterization of fire-retardant paint was achieved. **Materials and Methods:** The components used in the production of the paint include ammonium dihydrogen phosphate, melamine, urea, gum Arabic and paint base which were blended together. Agilent Technology Cary 630 Fourier Transform Infrared (FTIR) analyzer was used to determine the structural characterization of the fire-retardant paint. The flammability properties of the coated samples and pH of the paint were also determined. **Results:** The density of the paint to have values ranging from 1.046 to 1.066 g cm⁻³ while the pH values range from 5.05 to 4.90. The FTIR spectra confirmed the presence of -NH₂ amide group, C=O carbonyl group, C=C conjugated structure, C-O stretching of inorganic carbonate, CH aliphatic group and C-O of carbohydrate. The flammability measurement showed the burning rate to range from 2.227 to 1.25 mm sec⁻¹. The ignition times were found to range from 3 to 4 sec. The flame spread test values range from 6 to 8 sec. **Conclusion:** From the results of the burning analysis, Level 4 had the highest flame-retardant properties. There is a clear difference in the ignition time and burning rate of the coated samples compared to the uncoated reference.

KEYWORDS

Fire retardant, density, burning rate, ignition time, ammonium phosphate

Copyright © 2024 Amusan et al. This is an open-access article distributed under the Creative Commons Attribution License, which permits unrestricted use, distribution and reproduction in any medium, provided the original work is properly cited.

INTRODUCTION

Fire retardants are substances that are applied to the surface of any combustible base such as wood, bricks and metals to form a protective and decorative fireproof coating¹. Cellulosic base composites like plywood, particle boards and fiberboard are widely used in building constructions². These materials are highly combustible and often pose serious fire hazards³. Nowadays, the rapid changes in building and development in architecture and technology have led to more complex structures with a wide range of materials in the form of organic or inorganic and synthetic or natural materials used in buildings being easily flammable or readily burns on exposure to high temperature of fire⁴. On the other hand,



non-combustible materials such as metals and concrete will neither burn nor support combustion or release flammable vapors when subjected to fire. However, they can withstand fire for a certain period, making their strength deteriorate significantly at high temperatures. The devastating nature of fire creates havoc that results in great loss of both lives and properties. It can also cause great human suffering and financial losses. If these materials are suitably and properly treated for fire retardancy, it will decrease the growth period of fire and also reduce the spread of flame thereby preventing the occurrence of fire hazards and loss of life and properties. Traditionally, fire retardant coatings typically make use of compounds that contain halogenated compounds like chlorine and bromine⁵. The coatings formulated from these compounds are more effective in the gas phase and act in the flame zone by forming a blanket of halogen vapor that interferes with the propagation of flame that interrupts the generation of highly reactive free radicals, thus helping in extinguishing flame. However, the release of toxic and corrosive gases generated by these halogenated compounds while burning is ecologically unsafe, posing a lot of potential risks to human health and the environment^{6,7}. Recently fire retardants based on nitrogen compounds are found to be of interest to researchers due to their environmentally friendly nature. Nitrogen-based fire retardants have the following advantages, these include low toxicity, absence of dioxin and halogen acids and low evolution of smoke unlike halogen-based flame retardants, they do not interfere with the set of stabilizers added to the material^{8,9}. Also, fire retardants based on nitrogen compounds are suitable for recycling due to their high decomposition temperature. Moreover, they are environmentally friendly because they do not add any new elements to those already present in the polymer composition. Given the foregoing, this research work will focus on the production of nitrogen-based flame retardants synthesized from agricultural materials.

Research on the production of fire-retardant paints is very scarce; therefore, the objective of this research is to determine the ignition time, flame spread time, burning rate and percentage weight loss of fire-retardant paint produced from ammonium dihydrogen phosphate, melamine and urea.

MATERIALS AND METHODS

Study area and location: This research was conducted in the Chemistry Laboratory Nigerian Defence Academy, Igabi Local Government Area Kaduna, Nigeria. It is located on Latitude 10°609' and Longitude 7°429' North of the Greenwich meridian. The research was conducted within a period of seven months, From February, 2022 to September, 2022.

Sample collection: All the raw materials that were used for the production of the fire-retardant paint were locally sourced. Five kilogram of raw gum Arabic was purchased from Kawo Market, Kaduna. The wood that was used as substrate and urea was purchase from Mando Market. Ammonium dihydrogen phosphate was purchased from Nec. Nigeria Limited, Kano Road Kasua, Kaduna. While all other raw materials were purchased from Sunny Wax Paint, Tundun Wada Kaduna.

Materials: The industrial-grade chemicals that were used for the production of the fire retardants coating include the following: Melamine, urea, titanium dioxide, polyvinyl acetate, Calgon, nitosol, genepour, gum Arabic, calcium carbonate, formalin and ammonium dihydrogen phosphate (analytical grade).

Instrumentation: The equipment that was used in the course of the research included; HI8424 General purpose pH/mV Meter, Note Book series Digital scale, Binatone electric mixer; son: MPR/EEE/0042. stopwatch, methane source bunsen burner and Agilent Technology 380 FTIR analyzer.

Methods of Analysis

Preparation of the fire-retardant coating: The preparation of the fire-retardant coating was carried out by blending all the components together¹⁰.



Plate 1: Preliminary production of fire-retardant paint



Plate 2: Fire retardant paints produced

The coating was prepared as follows:

Level 1: A 500 cm³ of water at room temperature was measured into an electric mixer; 7.3 g of Calgon was added and mixed for 2 sec, then 11.20 g of titanium dioxide was added and mixed (for 1 sec), 16.90 g of calcium carbonate was added and mixed, then, 23.2 g of polyvinyl acetate, 7.6 g of urea, 1.1 g of nitrosol and 1.6 cm³ of gene pour with 0.7 cm³ of formalin were separately added and mixed for 2 sec. Then 22.80 g of ammonium phosphate was added and mixed for 1 sec and 7.60 g of melamine was added as shown in Plate 1. The mixture was mixed thoroughly for 5 sec and weighed. The paint produced was transferred into a container and covered tightly as shown in Plate 2.

The same procedure was followed for Levels 2, 3 and 4. The basic component of the fire-retardant paint was presented in Table 1 and the percentage composition of each component was presented in Table 2. The pictures of the fire-retardant paint produced were presented on Plate 1 and 2.

Basic components of fire-retardant paints and their function in the production: The following are the basic components for the production of fire-retardant paint and their respective roles:

- **Fire-retardant additives:** Include; ammonium dihydrogen phosphate which acts as the acid source, melamine and urea which acts as the blowing agent and gum Arabic which acts as the carbon source
- **Binders:** These include an inorganic resin, polyvinyl acetate and an organic polysaccharide compound, gum Arabic
- **Paint additives:** These include; titanium dioxide (pigment), calcium carbonate (paint base or filler), Calgon (dispersing agent or emulsifier), nitrosol (thickener), genepor and formalin (preservative) (Table 1)

Table 1: Basic components of the FRP and their function

| Components | Class of additive | Function |
|-------------------------------|--------------------------|--------------------------------|
| Ammonium dihydrogen phosphate | Fire retardant component | Acid source |
| Melamine | Fire retardant component | Blowing agent |
| Urea | Fire retardant component | Carbon source |
| Polyvinyl acetate | Paint additive | Binder |
| Gum Arabic | Paint additive | Binder |
| Titanium dioxide | Paint additive | Pigment |
| Calcium carbonate | Paint additive | Paint filler |
| Calgon | Paint additive | Dispersing agent or emulsifier |
| Nitrosol | Paint additive | Thickener |
| Genepor | Paint additive | |
| Formalin | Paint additive | Preservative |

Table 2: Percentage composition of fire-retardant coating

| | Weight for the formulations (%) | | | |
|--------------------|---------------------------------|---------|---------|---------|
| | Level 1 | Level 2 | Level 3 | Level 4 |
| Ammonium phosphate | 22.80 | 16.00 | 18.75 | 35.00 |
| Melamine | 7.60 | 12.00 | 12.50 | 5.00 |
| Urea (28% ammonia) | 7.60 | 12.00 | 18.75 | 20.00 |
| Polyvinyl acetate | 23.20 | 24.10 | 12.10 | 7.90 |
| Gum Arabic | 0.00 | 5.90 | 7.90 | 12.10 |
| Titanium dioxide | 11.20 | 6.20 | 6.20 | 2.20 |
| Calcium carbonate | 16.90 | 11.90 | 11.90 | 5.90 |
| Formalin | 0.70 | 0.80 | 0.90 | 1.00 |
| Nitrosol | 1.10 | 1.20 | 1.30 | 1.40 |
| Calgon | 7.30 | 7.40 | 7.50 | 7.60 |
| Genepour | 1.60 | 1.70 | 1.80 | 1.90 |

Table 3: Thickness of the wood substrate before and after coating

| Levels | Thickness of wood before coating (mm) | Thickness of wood after coating (mm) |
|--------|---------------------------------------|--------------------------------------|
| 1 | 8.99 | 9.31 |
| 2 | 8.66 | 9.06 |
| 3 | 8.45 | 8.45 |
| 4 | 7.67 | 8.25 |

Preparation of the Limba wood substrate: The wood (cellulose substrate) that was used for this research was first polished into a smooth and uniform surface and then cut into 15×10 mm long as shown in Plate 3 and 4. The thickness of the wood before coating was 8.99, 8.66, 8.45 and 7.67 mm and after coating was measured to be: 9.31, 9.06, 8.45 and 8.25 mm (Table 3).

Quality parameter test of the fire-retardant paint

Determination of the pH of the paint: The pH of the paint samples was measured with the aid of a pre-calibrated pH meter. All the measurements were carried out at room temperature.

Determination of the density of the paint: A 50 cm³ of the paint was measured using a measuring cylinder and weighed on a weighing balance. The density of the paint was then calculated by dividing the weight by the volume as given in Eq. 1:

$$\text{Density} = \frac{\text{Mass}}{\text{Volume}} \quad (1)$$

Determination of the percentage weight gain of the coated material: The coating weight gain percent of the coated wood was calculated as follows.



Plate 3: Measuring the thickness of wood substrate before coating



Plate 4: Coated woods with fire retardant paint

The weight gains percent of the coated materials and the weight of the uncoated reference were calculated using Eq. 2:

$$\text{Weight gain (\%)} = \frac{W_1 - W_0}{W_0} \times 100 \quad (2)$$

where, W_0 and W_1 are the weights of materials before and after coating.

Flammability measurement of the fire-retardant paint: A horizontal burning test was carried out to evaluate the burning rate and extent of the burning of the coated samples tested in a horizontal position according to the American Standard for Testing of Material, ASTM D 635-75 standard¹¹. The dimensions of the samples were 15×10×6 mm. Edge exposure was carried out when the flame was applied to the bottom edge of the test sample. The time taken to ignite the tiniest particle of the wood was taken as the ignition time. The burning rate and percentage weight loss of the coated samples were determined.

Chemical characterization of the fire-retardant paint: The active functional groups present in the paint were assessed by Fourier Transform Infrared (FTIR) analysis using Agilent Technology Cary 630 instrument at room temperature. The samples were scanned over a spectra range of 4000-650 cm^{-1} with a resolution of 8 cm^{-1} .

Statistical analysis: The data obtained were analyzed using Microsoft Excel and IBM SPSS (version 23). The dependent parameters were varied at four levels with each having three replicates. The average values were determined and applied as the representative data.

RESULTS AND DISCUSSION

Physico-chemical properties of the fire-retardant paint

pH of the fire-retardant paint: The pH values of the paint samples produced fall into the range of 5.05, 5.03 and 5.24 for Levels 1, 2 and 3, respectively, while Level 4 has a pH of 4.90 as shown in Fig. 1. This implied that fire-retardant paint is slightly acidic due to the composition of the fire-retardant paint. Research reported that samples that contain gum Arabic solution in their compositions had lower pH values as compared to samples that do not have¹². This shows gum Arabic also can lower the pH of paint.

It was reported in the literature that the standard value in paint production according to Standard Organization of Nigeria was a pH above 9.0¹³. Figure 1 showed the bar chart representation of the pH of the paint.

Effect of ammonium phosphate on the pH of the fire-retardant paint: Ammonium dihydrogen phosphate is also responsible for the reduced pH of the fire-retardant paint. Research showed that physicochemical properties like stability and shelf life of the paint (which is a direct function of its pH) were affected by the components used in manufacturing the paint¹⁴. From the result obtained, the pH of the paint decreases as the percentage of ADP increases. Level 4 which has the highest amount of ammonium dihydrogen phosphate has the lowest pH of 4.9. The graphical representation of pH against ammonium phosphate was shown in Fig. 2.

Weight gain percent of the coated material: The percentage weight gain of the coated samples was obtained as follows:

Level 1:

$$\begin{aligned} \text{Weight gain (\%)} &= \frac{8.0 - 7.1}{7.1} \times 100 \\ &= \frac{0.9}{7.1} \times 100 = 0.127 \times 100 = 12.68\% \end{aligned}$$

Level 2:

$$\begin{aligned} \text{Weight gain (\%)} &= \frac{8.4 - 6.9}{6.9} \times 100 \\ &= \frac{1.5}{6.9} \times 100 = 0.217 \times 100 = 21.74\% \end{aligned}$$

Level 3:

$$\begin{aligned} \text{Weight gain (\%)} &= \frac{7.1 - 6.6}{7.1} \times 100 \\ &= \frac{0.5}{7.1} \times 100 = 0.0704 \times 100 = 7.04\% \end{aligned}$$

Level 4:

$$\begin{aligned} \text{Weight gain (\%)} &= \frac{6.6 - 6.1}{6.4} \times 100 \\ &= \frac{0.3}{6.4} \times 100 = 0.0469 \times 100 = 4.68\% \end{aligned}$$

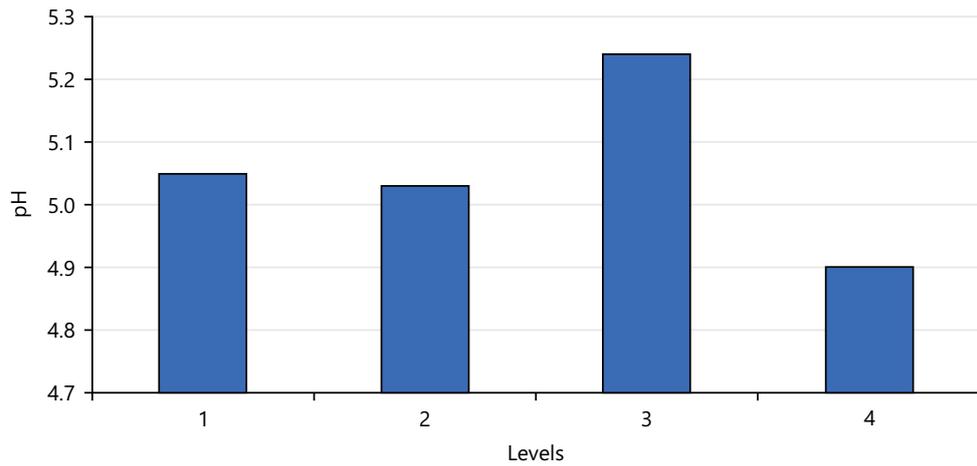


Fig. 1: Bar chart representations for the pH of FRP

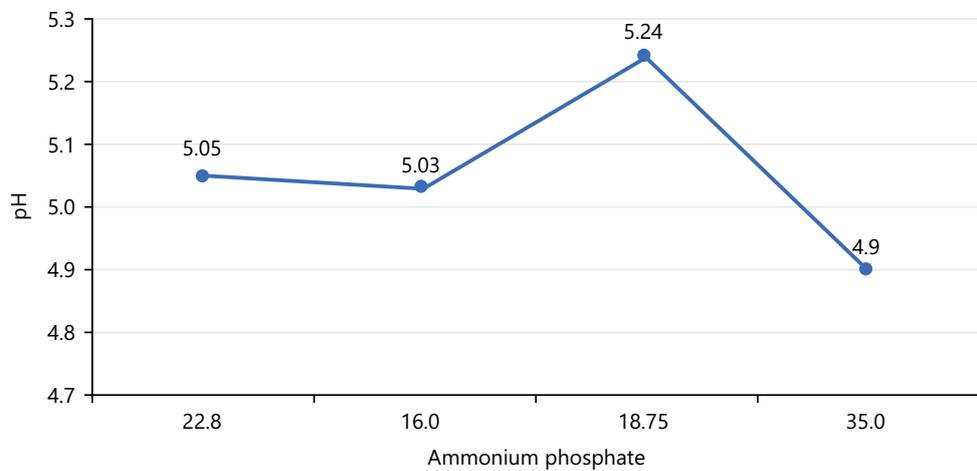


Fig. 2: Graph representation of pH against ammonium phosphate

Table 4: weight gain Percent of wood before and after coating

| Levels | Weight of wood before coating (g) | Weight of wood after coating (g) | Weight gain (%) |
|--------|-----------------------------------|----------------------------------|-----------------|
| 1 | 7.1 | 8.0 | 12.68 |
| 2 | 6.9 | 8.4 | 21.74 |
| 3 | 6.6 | 7.1 | 7.04 |
| 4 | 6.1 | 6.4 | 4.68 |

From the result obtained, Level 2 has the highest percentage of weight gain. Due to the highest percentage of binders (polyvinyl acetate) in its composition. This showed that Level 2 adheres to the substrate better and has better applicability on the wood. Table 4 shows the percentage weight gain of the coated samples.

Density of the fire-retardant paint: The density of the paint was obtained as follows:

Level 1:

$$\text{Density} = \frac{\text{Mass}}{\text{Volume}} = \frac{46.2 \text{ g}}{50 \text{ mL}} = 0.924 \text{ g cm}^{-3}$$

Level 2:

$$\text{Density} = \frac{\text{Mass}}{\text{Volume}} = \frac{52.8 \text{ g}}{50 \text{ ml}} = 1.056 \text{ g cm}^{-3}$$

Level 3:

$$\text{Density} = \frac{\text{Mass}}{\text{Volume}} = \frac{51.6 \text{ g}}{50 \text{ mL}} = 1.032 \text{ g cm}^{-3}$$

Level 4:

$$\text{Density} = \frac{\text{Mass}}{\text{Volume}} = \frac{52.7 \text{ g}}{50 \text{ mL}} = 1.054 \text{ g cm}^{-3}$$

The density of the paint samples produced fell within the specified range by ENISO 2811-1 Standard. From the result obtained, Level 1, has a density of 0.924 g cm^{-3} , while Levels 2, 3 and 4 have higher densities of 1.056 , 1.032 and 1.054 g cm^{-3} , respectively (Table 4) due to the presence of gum Arabic in the component of the paint. Level 1 which has the lowest density has 0% gum Arabic. This showed that gum Arabic has a contributing factor in increasing the density of the paint¹⁵. Figure 3 shows the bar chart representation of the density of the paint.

Effect of gum Arabic on the physicochemical properties of the fire-retardant paint: Gum Arabic has a pH range between 4.5 to 5.0¹⁶. The density and brightness of the paint change as the percentage of gum Arabic increases. Level 1 which has 0% gum Arabic has the lowest density of 0.49 g cm^{-3} and the brightest color while Levels 2, 3 and 4 have an increased density and dull color. This was similar to what Abdulsalam and Maiwada¹⁵ obtained in their results.

Fire performance with horizontal burning test: Table 5 shows the ignition time, flame spreading time, burning rate, the extent of burning and percentage weight loss of the coated wood samples. The ignition time for control and Levels 1, 2, 3 and 4 were 2, 3, 3, 4 and 4 sec and the burning rate for control and Levels 1, 2, 3 and 4 was 0.033 , 0.015 , 0.016 , 0.008 and 0.009 g sec^{-1} , respectively. There is an average decrease of 63.6% in the burning rate of the uncoated samples compared to the coated sample. Ofuyatan *et al.*¹⁷, reported a decrease of 48.9% in the burning rate of a sample coated with fire retardant paint¹⁷. Research showed that the flame propagation rate and after glow time of both emulsion and gloss coated wood splints decreased with increase in concentration of the fire retardant. On the other hand, the ignition time was increased^{18,19}.

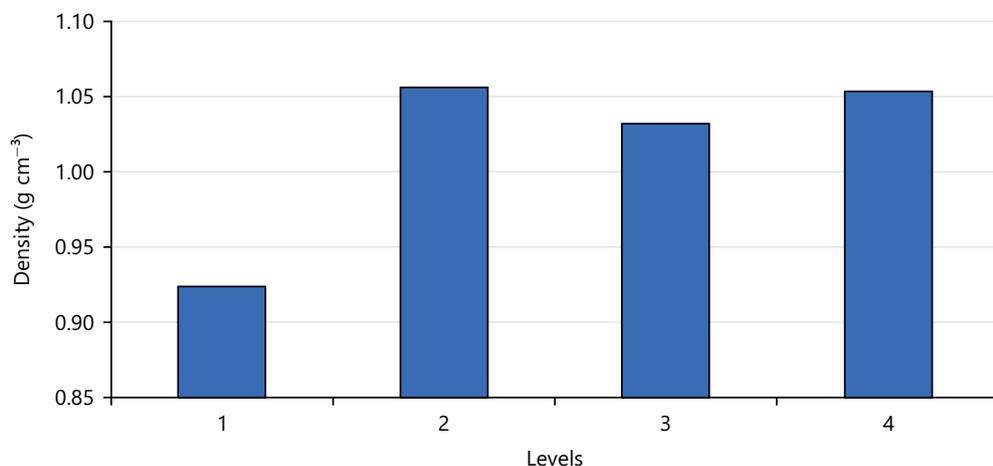


Fig. 3: Bar chart representations for the density of FRP

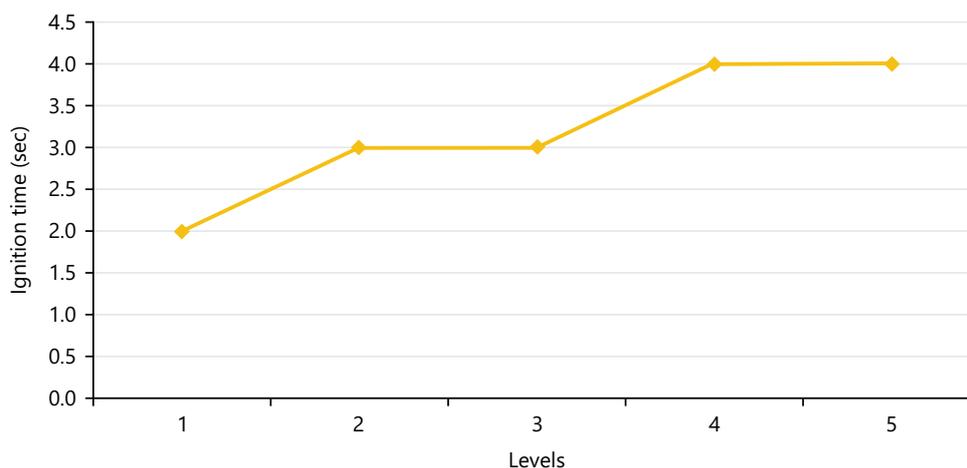


Fig. 4: Graphical representation of the ignition time of FRP

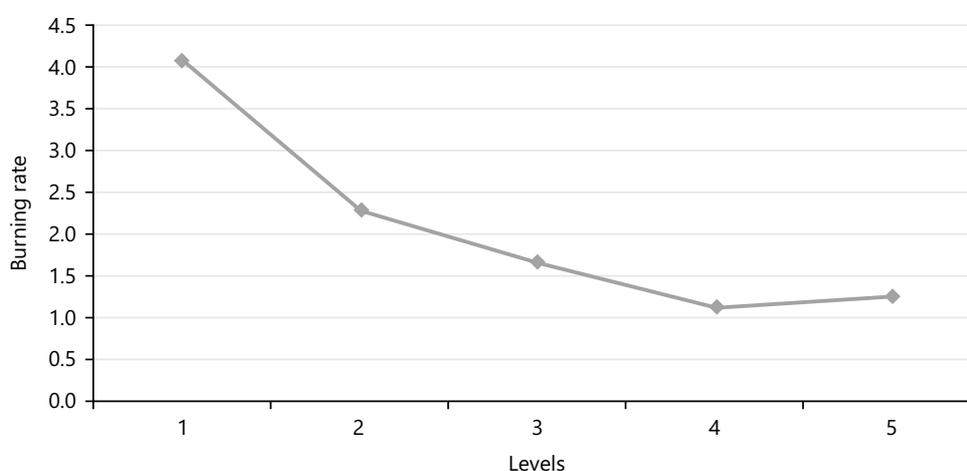


Fig. 5: Graphical representations of the burning rate of the FRP

Table 5: Fire performance of the FRP


| Level | Ignition time (sec) | Flame spread (sec) | Burning rate (g sec ⁻¹) | Weight loss (g) | Weight loss (%) |
|---------|---------------------|--------------------|-------------------------------------|-----------------|-----------------|
| Control | 2 | 2 | 0.033 | 0.13 | 1.85 |
| L 1 | 3 | 3 | 0.015 | 0.09 | 1.15 |
| L 2 | 3 | 4 | 0.016 | 0.11 | 1.31 |
| L 3 | 4 | 4 | 0.008 | 0.06 | 0.84 |
| L 4 | 4 | 4 | 0.009 | 0.07 | 1.11 |

Comparison between the burning rate and the ignition time of the fire-retardant paint: From the result of the analysis, the flame spread between 3-4 sec after ignition and the total burning time was 6, 7, 8 and 8 sec for Levels 1, 2, 3 and 4, respectively. This implies that when the coatings have burnt for these times only 0.09, 0.11, 0.06 and 0.07 g of the substrate got burnt at a very slow rate. This complied with the mechanism of an ideal fire-retardant coating as reported by Mariappan⁴ in his report. The purpose of the fire-retardant paint is to stop flame propagation and prevent the substrate from being consumed. The burning rate of the coated samples slowed down compared to the control. Level 4 has the lowest burning rate. Figure 4 and 5 showed the graphical representation of the ignition time and burning rate of the fire-retardant coating.

Effect of ammonium phosphate, melamine, gum Arabic and urea on the flammability properties of the fire-retardant paint: When the active components of the fire-retardant paint i.e., ammonium dihydrogen phosphate (a catalyst), melamine (blowing agent), gum Arabic and urea

(carbonaceous materials) are exposed to fire, the ammonium phosphate decomposes to produce phosphoric acid which acts as a dehydrating agent. The polysaccharide salt (gum Arabic) upon hydrolysis with the help of melamine and urea is dehydrated by the acid-forming a large amount of carbonaceous material that form a noncombustible barrier to protect the wood substrate from burning. As a result, flame propagation is stopped. Thus, making the flame spread time and the burning rate of the coated substrate slow down. Weil²⁰ reported the interaction of melamine with phosphorus acid by the decomposition of ammonium phosphate which leads to the generation of ammonia gas and the formation of melamine phosphate salts.

The combustion reaction of ammonium phosphate which takes place within the paint on heating is given in Eq. 3:



Structural characterization of the fire-retardant paint: The chemical structure of the FRP components was confirmed by FTIR. There is a broad Peak at 3265, 3257 and 3272 cm^{-1} which confirms the presence of an amide- NH_2 group from melamine and urea. The characteristic peak around 2119 cm^{-1} (Level 1), 2112 cm^{-1} (Level 2), 2109 cm^{-1} (Level 3) and 2117 cm^{-1} (Level 4) is attributed to the C=C of a conjugated structure coming from the presence of polyvinyl acetate. Also, there is a sharp peak around 1636 cm^{-1} (Levels 1, 2, 3 and 4), which is attributed to C=O of a carbonyl group from urea and polyvinyl acetate. The peak at 1457 cm^{-1} (Level 1), 14553 cm^{-1} (Level 2) and 1461 cm^{-1} (Levels 3 and 4) is attributed to C-O stretching of an inorganic carbonate coming from calcium carbonate. The disappearing peak around 1364 cm^{-1} (Level 1) and 1371 cm^{-1} (Level 2) is attributed to CH bending of an aliphatic group which is coming from the presence of gum Arabic and polyvinyl acetate. Also, the strong peak at 1069 cm^{-1} (Levels 1 and 4) and 1073 cm^{-1} (Level 3) is attributed to the C-O of a carbohydrate which is also coming from gum Arabic. Summarily, the result of the FTIR showed that the existence of all these bonds and functional groups indicates the presence of all the active ingredients necessary for the flame retardancy of the paint produced.

Given future research, the following recommendations were made:

- It is recommended that a gloss-type fire retardant paint should be employed for wood and cellulose substrate for the paint to have better adhesion with high water resistance
- To prolong the shelf life of the paint and for better stability, the pH of the paint needs to be adjusted to above 9.0 by increasing the percentage of CaCO_3 or by adding soda ash and more preservatives
- To increase the ignition time and lower the burning rate of the paint, the percentage of ammonium phosphate should be increased and it must be ensured that all the chemicals are still potent and within their shelf life

CONCLUSION

The gum Arabic can be used in conjunction with polyvinyl acetate as binder in the production of fire-retardant paint. This would lower the cost of production since the cost of gum Arabic is lower than that of polyvinyl acetate. Also, ammonium dihydrogen phosphate, melamine, gum Arabic and urea are effective in offering fire retardant properties in the production of emulsion-type fire retardant paint. The density of the paint samples produced fell within the specified range by ENISO 2811-1 Standard. The pH of the paint is lower than that of the ENISO standard as a result of the composition of the paint, this could make the paint to be susceptible to bacterial growth after a long time.

SIGNIFICANCE STATEMENT

The environmental pollution originating from non-biodegradable synthetic fire-retardant polymers produced industrially is on the increase, there is a need for environmentally friendly fire retardants for surface coating which can be decorative as well as in the case of a fire it can effectively reduce the surface burning rate of the combustible structure, thereby prevent a small fire from developing into a major one and giving enough time for people to evacuate their valuables and rescuers to organize rescue efforts. It is intended that the use of bio-degradable polymers made from gum Arabic, ammonium phosphate, melamine and urea will contribute to a sustainable reduction in environmental hazards and reduction in the accumulation of synthetic polymer-based fire retardant residue in the environment.

REFERENCES

1. Luo, J., 2016. Ignition properties of panels coated with finishing fire-retardant paints under external radiation. *Procedia Eng.*, 135: 123-127.
2. Cavdar, A.D., S.B. Torun, M. Ertas and F. Mengeloglu, 2019. Ammonium zeolite and ammonium phosphate applied as fire retardants for microcrystalline cellulose filled thermoplastic composites. *Fire Saf. J.*, 107: 202-209.
3. Saxena, N.K. and D.R. Gupta, 1990. Development and evaluation of fire retardant coatings. *Fire Technol.*, 26: 329-341.
4. Mariappan, T., 2017. Fire Retardant Coatings. In: *New Technologies in Protective Coatings*, Giudice, C. and G. Canosa (Eds.), InTechopen, London, UK, ISBN: 978-953-51-4668-1.
5. Shaw, S., 2010. Halogenated flame retardants: Do the fire safety benefits justify the risks? *Rev. Environ. Health*, 25: 261-306.
6. Alongi, J., J. Tata and A. Frache, 2011. Hydrotalcite and nanometric silica as finishing additives to enhance the thermal stability and flame retardancy of cotton. *Cellulose*, 18: 179-190.
7. Zheng, C., D. Li and M. Ek, 2019. Improving fire retardancy of cellulosic thermal insulating materials by coating with bio-based fire retardants. *Nordic Pulp Pap. Res. J.*, 34: 96-106.
8. Qiao, Y., Y. Wang, M. Zou, D. Xu, Y. Pan, Z. Luo and B. Wang, 2019. One-step synthesis of highly efficient oligo (phenylphosphonic dihydroxypropyl silicone oil) flame retardant for polycarbonate. *Polymers*, Vol. 11. 10.3390/polym11121977.
9. Horacek, H. and R. Grabner, 1996. Advantages of flame retardants based on nitrogen compounds. *Polym. Degrad. Stab.*, 54: 205-215.
10. Idris, M.N. and J.A. Rashan, 2017. Laboratory studies on small scale production of three (3) different grades of emulsion paints. *Res. J. Pure Sci. Technol.*, 1: 23-35.
11. Hossain, M.D., M. Kamrul Hassan, A.C.Y. Yuen, Y. He, S. Saha and W. Hittini, 2021. Flame behaviour, fire hazard and fire testing approach for lightweight composite claddings-A review. *J. Struct. Fire Eng.*, 12: 257-292.
12. Ocheri, C., J.B. Agboola and O.M. Moses, 2017. Investigation of gum Arabic and its suitability as a composite binder for core production. *J. Powder Metall. Min.*, Vol. 6. 10.4172/2168-9806.1000147.
13. Orjiakor, P.I., C.N. Eze and A.S. Aladetoyinbo, 2019. Physicochemical quality and mycodegradation of commercial paint effluents from factories in Ado-Ekiti, Southwestern Region, Nigeria. *FUTY J. Environ.*, 13: 98-111.
14. Ndibe, H.C., J.U. Iyasele, E.O. Imanah, G.E. Okpara and I. Eriamiatoe, 2021. Utilization of binary blends of liquid natural rubber and polyvinyl acetate in emulsion paint. *J. Chem. Soc. Nigeria*, 46: 72-78.
15. Abdulsalam, S. and Z.D. Maiwada, 2015. Production of emulsion house paint using polyvinyl acetate and gum Arabic as binder. *Int. J. Mater. Sci. Appl.*, 4: 350-353.
16. Yaumi, A.L., A.M. Murtala, H.D. Muhd and F.M. Saleh, 2016. Determination of physicochemical properties of Gum Arabic as a suitable binder in emulsion house paint. *Int. J. Environ.*, 5: 67-78.

17. Ofuyatan, O., T. Gbolade, A. Adeniyi, J. Ighalo and J. Oluwafemi, 2021. Evaluation of fire-retardant properties of emulsion, text-coat and gloss paints modified with bio-based extract of *Acalypha wilkesiana*. IOP Conf. Ser.: Mater. Sci. Eng., Vol. 1036. 10.1088/1757-899X/1036/1/012077.
18. Arinze, R.U., A.N. Eboatu, P.I. Udeozo, J.I. Dioha and U.I. Okoye, 2015. Flame retardant paint treatment of some tropical timbers. Eur. J. Appl. Sci., 7: 195-198.
19. Rosemary, U.A., N.E. Augustine, H.O. Nkechi, U.O. Pauline, I.U. Pascaline and C.A. Joseph, 2014. Studies on the effectiveness of flame retardant paint treatment of timbers. Middle-East J. Sci. Res., 21: 1652-1654.
20. Weil, E.D., 2011. Fire-protective and flame-retardant coatings-A state-of-the-art review. J. Fire Sci., 29: 259-296.